

Limitless silanes

**Bonding organic and
inorganic materials**

DOW

®





03	The first in silane development
03	What is a silane?
03	Functions and benefits
04	Why silane coupling agents are used
05	Silane product overview (Fold out)
07	Bonding to inorganic substrates
07	Bonding to polymers
07	Selecting the right silane



08	Water repellents and surface protection
09	Surface protection



10	Plastics and composites (Including fiberglass)
10	Rubber compounding
10	Plastics compounding
10	Fiberglass-reinforced polymers



12	Paints, inks and coatings
12	Primers
12	Automotive clearcoats
13	Architectural coatings
13	Industrial coatings



14	Adhesives and sealants
14	Adhesion promoters
14	Coupling agents



15	Mineral and filler treatments
-----------	--------------------------------------






The first in silane development

Dow pioneered the development of silanes – and the synergy of organic and silicon chemistries – more than 60 years ago. Today, they remain instrumental in allowing new materials to be developed in a wide variety of industries with greater reliability and improved performance. And Dow continues to be a leader in developing and supplying silane solutions.

What is a silane?

A silane is a molecule comprised of one central silicon atom with four attachments. These substituent groups can be nearly any combination of nonreactive, inorganically reactive, or organically reactive groups. Silanes are the smallest silicon-based molecules, ensuring good depth of penetration into substrates. A silane that contains at least one carbon-silicon bond structure is known as an organosilane. In many applications, the term “silane” is a generic term typically referring to an organofunctional alkoxy silane. Here, the terms silane, alkoxy silane and organofunctional alkoxy silane are used interchangeably. They react with themselves and any hydroxyl (OH) groups within the substrate, often when moisture is present, forming a silicone resin network. This formation of strong chemical bonds provides durability.

Figure 1: The silane coupling mechanism

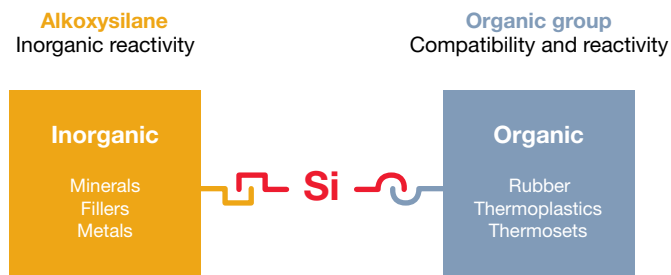

Functions and benefits

Silanes enable the development of new materials with greater reliability and improved performance. Silanes can function in many different ways to achieve various benefits, which include:

Coupling agent

Silane coupling agents are silicon-based chemicals that contain two types of reactivity – inorganic and organic in the same molecule. A silane coupling agent will act as an interface between an inorganic substrate (such as glass, metal or mineral) and an organic material (such as an organic polymer, coating or adhesive) to bond the two dissimilar materials.

Adhesion promoter

Silanes are effective adhesion promoters when used as additives or primers for paints, inks, coatings, adhesives and sealants. By using the right silane coupling agent, a paint, ink, coating, adhesive or sealant can be converted to a material that often will maintain adhesion even if subjected to severe environmental conditions.

Hydrophobing and dispersing agent

Alkoxysilanes with hydrophobic organic groups attached to silicon will impart that same hydrophobic character to a hydrophilic inorganic surface. They are used as durable hydrophobing agents in construction, bridge and deck applications. They are also used to hydrophobe inorganic powders to make them free-flowing and dispersible in organic polymers and liquids. Generally, alkoxy silanes are not effective at hydrophobing unfilled plastics.

Moisture scavenger


The alkoxy groups of silanes will hydrolyze in the presence of moisture to convert water molecules to alcohol molecules. Organotrialkoxysilanes are often used in sealants and other moisture-sensitive formulations as water scavengers.

Silicate stabilizer


Functions as a silicate stabilizer to prevent agglomeration and precipitation of silicates during use. The predominant application is in engine coolant formulations to stabilize the silicate corrosion inhibitors.



Figure 2: SEM image of silica-filled epoxy resin

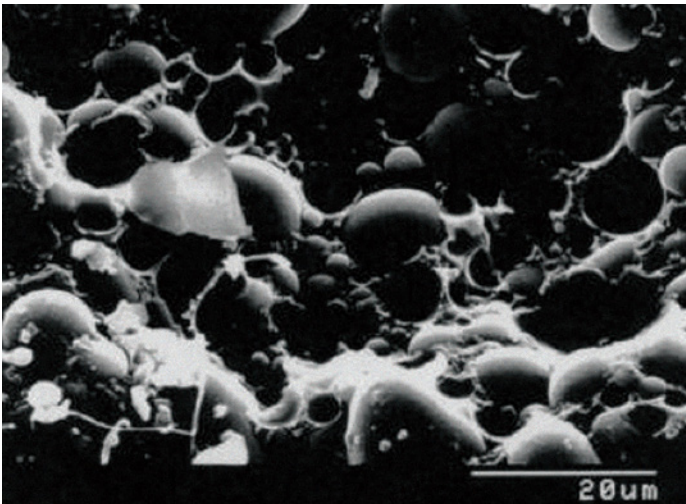

Without silane

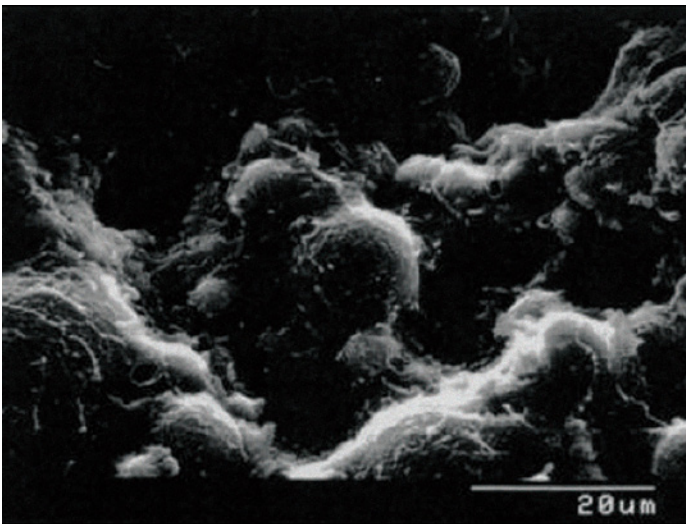

With silane

Why silane coupling agents are used


When organic polymers are reinforced with glass fibers or minerals, the interface, or interphase region between the polymer and the inorganic substrate, is involved in a complex interplay of physical and chemical factors. These factors are related to adhesion, physical strength, coefficient of expansion, concentration gradients and retention of product properties.

Silane coupling agents have the unique chemical and physical properties to not only enhance bond strength, but also prevent de-bonding at the interface due to use and aging, especially in humid conditions. The coupling agent provides a stable bond between two otherwise poorly bonding surfaces. Figure 2 shows (via an SEM of the fracture surface) the difference in adhesion between a silica-filled epoxy resin with silane versus without silane. With silane, the epoxy coating on the silica particles is apparent; without silane, clean silica particles can be seen in the epoxy matrix.

Silane coupling agents also increase the resistance to humidity and other adverse environmental conditions encountered by composites. Other benefits of silane coupling agents include:

- Better wetting of inorganic substrates
- Lower viscosities during compounding
- Smoother surfaces of composites
- Less catalyst inhibition of thermoset composites
- Clearer reinforced plastics

Figure 3: Hydrolysis of alkoxy silanes

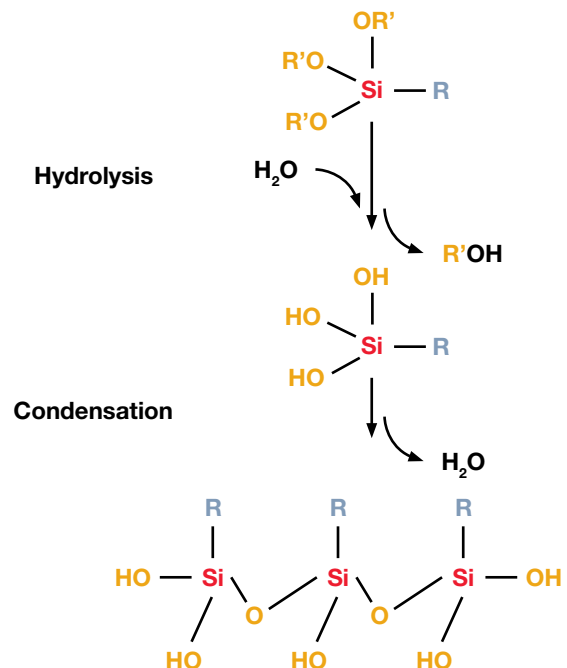

Silane product overview

Bonding organic and inorganic materials

[Back to Table of Contents](#)

Product name	Functionality	Chemical description	CAS #	Applications				
				Water repellents and surface protection	Plastics and composites	Paints, inks and coatings	Adhesives and sealants	Mineral and filler treatment
DOWSIL™ 11-100 Additive	Alkyl	Alkyl functional siloxane	N/A	•	•			•
XIAMETER™ OFS-1579 Silane	Alkyl	Methyl and ethyl triacetoxysilane	4253-34-3 and 17689-77-9				•	
XIAMETER™ OFS-6070 Silane	Alkyl	Methyltrimethoxysilane; CH ₃ -Si(OCH ₃) ₃ ; MTMS	1185-55-3				•	
XIAMETER™ OFS-6341 Silane	Alkyl	n-Octyltriethoxysilane; C ₈ H ₁₇ Si(OC ₂ H ₅) ₃ ; nOTES	2943-75-1	•				•
XIAMETER™ OFS-6665 Silane	Alkyl	n-Octyltrimethoxysilane; nOTMS	3069-40-7	•				•
XIAMETER™ OFS-6403 Silane	Alkyl	Butyl triethoxysilane; iBTES	17980-47-1	•				
XIAMETER™ OFS-2306 Silane	Alkyl	Butyl trimethoxysilane; iBTMS	18395-30-7	•				
DOWSIL™ Z-6701 Silane	Alkyl	Methyldimethoxysilane CH ₃ Si(H)(OCH ₃) ₂	16881-779		•			
XIAMETER™ OFS-6264 Silane	Alkyl	N-propyl trimethoxysilane; nPTMS	1067-25-0	•				
DOWSIL™ 1-6184 Water Repellent	Alkyl	Water-soluble siloxane	N/A	•				
DOWSIL™ Z-6689 Water Repellent	Alkyl	Silane/siloxane blend	N/A	•				
DOWSIL™ Z-6690 Water Repellent	Alkyl	Silane/siloxane blend	N/A	•				
XIAMETER™ OFS-0772 Siliconate	Alkyl	Sodium methyl siliconate	16589-43-8	•				
XIAMETER™ OFS-0777 Siliconate	Alkyl	Potassium methyl siliconate	31795-24-1	•				
XIAMETER™ OFS-6011 Silane	Amino	Aminopropyltriethoxysilane; H ₂ NC ₃ H ₆ -Si(OC ₂ H ₅) ₃	919-30-2		•	•	•	•
XIAMETER™ OFS-6020 Silane	Amino	Aminoethylaminopropyltrimethoxysilane; H ₂ NC ₂ H ₄ NHC ₃ H ₆ -Si(OCH ₃) ₃ ; AEAPTMS	1760-24-3		•	•	•	•
DOWSIL™ Z-6137 Silane	Amino	Aminoethylaminopropylsilane; Triol homopolymer; H ₂ NC ₂ H ₄ NHC ₃ H ₆ -Si(OH) ₃ in water 22% actives; Low methanol content; Pre-hydrolyzed version of XIAMETER™ OFS-6020 Silane	68400-09-9		•	•		
DOWSIL™ Z-6121 Silane	Amino	Aminoethylaminopropyltrimethoxysilane; H ₂ NC ₂ H ₄ NHC ₃ H ₆ -Si(OCH ₃) ₃ ; 50% actives in n-butanol/methanol	1760-24-3		•	•		
XIAMETER™ OFS-6032 Silane	Amino/Vinyl	Vinylbenzylaminoethylaminopropyltrimethoxysilane; (H ₂ C=CHC ₆ H ₄ -CH ₂ -NHC ₂ H ₄ NHC ₃ H ₆ -Si(OCH ₃) ₃); HCl 40% in methanol	171869-89-9		•	•		
DOWSIL™ Z-6269 Silane	Amino/Vinyl	Cationic vinylbenzyl and amino functional methoxysilane; 40% actives in methanol; Higher actives purity version	171869-89-9		•			
DOWSIL™ Z-6132 Silane	Amino/Vinyl	Hydrolyzed version of XIAMETER™ OFS-6032 Silane; 37% solids in methanol	171869-90-2		•			
XIAMETER™ OFS-6224 Silane	Amino/Vinyl	Vinylbenzylaminoethylaminopropyltrimethoxy silane; (H ₂ C=CHC ₆ H ₄ -CH ₂ -NHC ₂ H ₄ NHC ₃ H ₆ -Si(OCH ₃) ₃); Partially hydrolyzed at 33% in methanol; Low chloride	171869-90-2		•			
XIAMETER™ OFS-6062 Silane	Mercapto	3-Mercaptopropyltrimethoxysilane; HS(CH ₂) ₃ Si(OCH ₃) ₃ ; MPTMS	4420-74-0		•			
XIAMETER™ OFS-6040 Silane	Epoxy	Glycidoxypropyltrimethoxysilane; CH ₂ (O)CHCH ₂ OC ₃ H ₆ -Si(OCH ₃) ₃ ; GPTMS	2530-83-8		•	•	•	•
XIAMETER™ OFS-6030 Silane	Methacryl	Methacryloxypropyltrimethoxysilane; H ₂ C=CH(CH ₃)C(O)OC ₃ H ₆ -Si(OCH ₃) ₃ ; MAPTMS	2530-85-0		•	•	•	•
DOWSIL™ Z-6883 Silane	Phenyl/Amino	Phenylaminopropyl trimethoxysilane; PhNHC ₃ H ₆ Si(OCH ₃) ₃	3068-76-6		•			
XIAMETER™ OFS-6124 Silane	Phenyl	Phenyltrimethoxysilane; (C ₆ H ₅ -Si(OCH ₃) ₃)	2996-92-1			•		•
XIAMETER™ OFS-6697 Silane		Tetra ethoxysilane; TEOS	78-10-4	•				•
XIAMETER™ Q1-6083 Antifreeze Additive		Phosphonate sodium siliconate; 40% sodium (trihydroxysilyl)-propylmethosphonate in water	84962-98-1					• (Engine coolant)

Bonding to inorganic substrates

Silane coupling agents that contain two or three inorganic reactive groups on silicon will bond well to the hydroxyl groups on most inorganic substrates, especially if the substrate contains silicon, aluminum or a metal in its structure. The alkoxy groups on silicon hydrolyze to silanols, either through the addition of water or from residual water on the inorganic surface. Then the silanols coordinate with metal hydroxyl groups on the inorganic surface to form an oxane bond and eliminate water.

Bonding to polymers

The bond to the organic polymer is complex. The reactivity of a thermoset polymer should be matched to the organo-reactivity of a silane. To optimize the inter-penetrating network bonding mechanism, it is important that the silane and the resin be compatible. Matching the chemical characteristics of the two materials will help improve the chances of forming a good composite with optimum benefits.

Selecting the right silane

The choice of silane should involve matching chemical reactivity, solubility characteristics and, possibly, the thermal stability of the organosilane with the same parameters in the polymer structure.

Figure 4: The inter-penetrating network (IPN) bonding mechanism



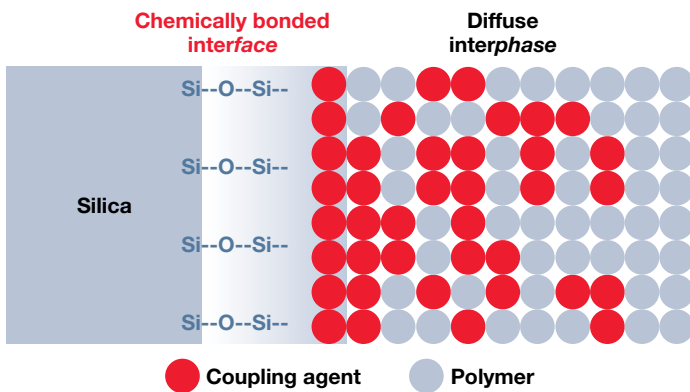



Figure 5: Basic structure R= alkyl, aryl, or organofunctional group OR'= methoxy, ethoxy, or acetoxy

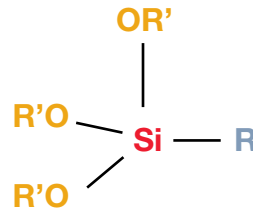


XIAMETER™ OFS-6011 Silane

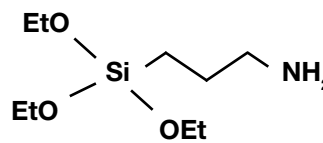


XIAMETER™ OFS-6030 Silane

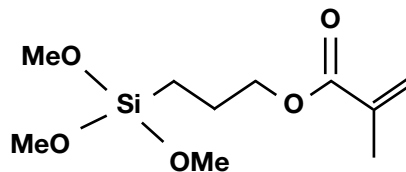


XIAMETER™ OFS-6032 Silane

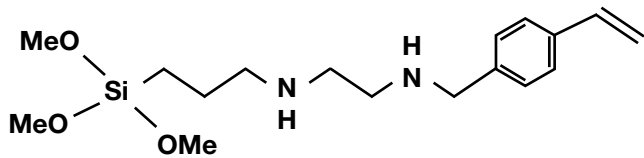

XIAMETER™ OFS-6040 Silane

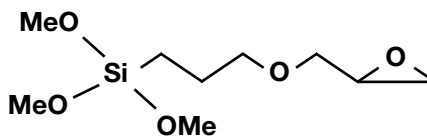

XIAMETER™ OFS-6341 Silane

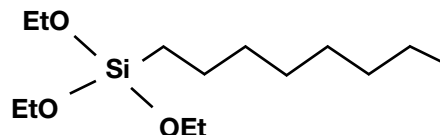

Silane product overview

Bonding organic and inorganic materials

(Fold out)




[Back to Table of Contents](#)

Water repellents and surface protection

Nature can be a tough adversary – water intrusion, sunlight, wind and abrasion, infiltration of organisms, or even accidental stain damage. Silanes can give water- and stain-repellent properties to surfaces. Alkoxysilyl groups attached to these silanes allow them to penetrate, cure in and bond to many inorganic substrates. These unique properties allow for versatile and durable solutions to protect against harmful water- and oil-borne elements.

- Water vapor permeability
- High dilution capability and stability
- Clear, uniform, neutral appearance
- Reduced efflorescence
- Reduced freeze/thaw damage
- Chloride ion resistance to deter corrosion of reinforcing steel concrete structures
- Preservation of aesthetics
- Strengthening fragile masonry
- Dimensional stability of wood

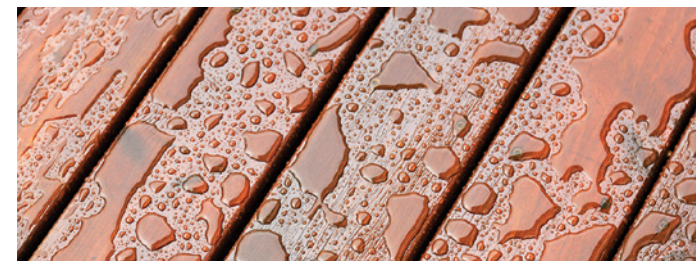

Silane-based water repellents create an envelope of protection that extends the life of substrates for years in challenging environments. Benefits may include:

- Excellent water repellency
- Long-term durability
- UV stability
- Depth of penetration

Whether you're looking for a fully formulated water or stain repellent, or a key ingredient in your surface protection formula, Dow offers a wide range of silanes that can meet your needs. Our water and stain repellent materials can be used in solvent or water-based systems to provide the formulating flexibility needed to meet VOC and ease-of-use requirements, and are available for use in formulations that penetrate a broad range of substrates, including:

- Poured-in-place or pre-cast concrete
- Concrete block
- Sandstone/granite
- Brick/tile/grout
- Wood
- Gypsum/perlite
- Limestone/marble

Surface protection

Dow also manufactures a range of silicates and siliconates for use in formulating pore-blocking sealers and consolidators.

Sealers include pore blockers, which form a resin barrier on concrete surfaces, partially or fully filling the surface pores; and hydrophobing agents, which deeply penetrate the material yet allow concrete to breathe and won't interfere with concrete cure.

Consolidators can extend the life of stone and concrete because they penetrate and cure in and through these materials to help bind them together. They are used in a variety of restoration and flooring applications.

Figure 6: Silicone-based products penetrate deeply, forming a repellent layer within the substrate


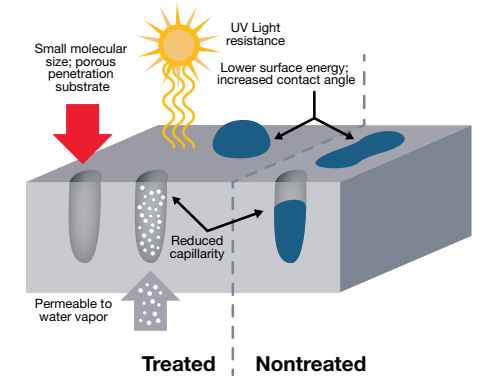


Figure 7: SiOH groups chemically bond to the substrate and condense to form a polymer film on the surface



Product name	General description	Application/features	Dilution system	Typical actives usage level %	Specific gravity	Flash point	Substrate						
							Concrete	Mortar and brick	Stone	Ceramics	Wood	Anti-stain	Damp proofing
XIAMETER™ OFS-6341 Silane	Alkyl ethoxy silane	Effective hydrophobing agent and high-temperature additive for other coupling agents	Solvent	5 to 100	0.88	65	•	•	•				•
XIAMETER™ OFS-6665 Silane	Alkyl methoxy silane	Effective hydrophobing agent that inhibits water absorption and can be used in formulation of water repellent products	Solvent	5 to 100	0.91	66	•	•	•				•
XIAMETER™ OFS-6403 Silane	Butyl triethoxysilane	Protection against chloride ion intrusion in concrete	Solvent	5 to 100	0.88	62	•	•	•				
XIAMETER™ OFS-2306 Silane	Butyl trimethoxysilane	Ideal for treating a variety of substrates to impart water repellency and compatibility with organics	Solvent	5 to 100	0.92	32	•	•	•				
XIAMETER™ OFS-6697 Silane	Tetra ethoxysilane; TEOS	Diluent for zinc-rich primers • Additive for other coupling agents	Solvent	5 to 100	0.93	54	•	•	•				
DOWSIL™ Z-6689 Water Repellent	Solventless silane/siloxane blend	Active component for formulating penetrating water repellent treatments • Multi-surface water repellent • For neutral and alkaline mineral substrates that require water repellency • Excellent beading in <5 minutes • Dilutable in organic solvent to formulate water repellent products	Solvent	5 to 15	0.96	10							•
DOWSIL™ Z-6690 Water Repellent	Silane/siloxane blend	Multi-surface water repellent • Low viscosity blend • Easy to apply • Designed for water-free formulations • Quick absorption on wood surface • Impregnation of wood surface provides low impact on appearance and surface tack • Not film forming	Solvent	5 to 15	0.94	37					•		
XIAMETER™ OFS-6264 Silane	Alkyl methoxy silane	Hydrophobing and dispersing agent	Solvent	5 to 100	0.93	26.6	•	•	•				
DOWSIL™ 1-6184 Water Repellent	Water-soluble silane	Low-VOC • Multifunctional • Self-crosslinking	Water	3.5 to 7.5	1.05	27					•		•
XIAMETER™ OFS-0772 Siliconate	Sodium methyl siliconate	Water dilutable • Effective on a variety of substrates	Water	0.5 to 3	1.25	>100			•		•		
XIAMETER™ OFS-0777 Siliconate	Potassium methyl siliconate	Water dilutable • Effective on a variety of substrates	Water	0.5 to 3	1.29	>100			•		•		

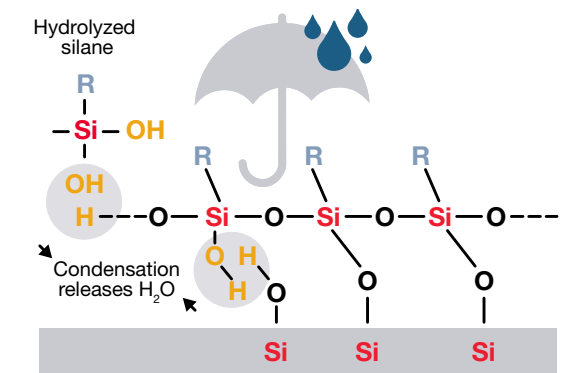

[Back to Table of Contents](#)

Plastics and composites (Including fiberglass)

Whether you need performance enhancements or process improvements, the unique properties of silanes can provide the solution. Silanes are critical to the strength and durability of composites and can provide more effective coupling and dispersion treatments as well as greater protection against environmental conditions.

Silanes from Dow:

- Enhance the mechanical and electrical properties of fiberglass-reinforced polymers
- Improve resistance to moisture attack at the interface
- Increase the strength and durability of composites under wet and dry conditions
- Provide wet-out and lubrication to the glass fiber
- Boost fiber strand integrity, production and handling
- Achieve reliable performance in cycling tests from hot to cold extremes

Rubber compounding

As demand increases for elastomeric products in colors other than black, and with the mechanical attributes similar to those provided by carbon black, silanes are the key to providing a method of effectively bonding various inorganics to the polymer phase.

Plastics compounding

Silanes have been used to improve filler dispersion and glass fiber incorporation into thermoplastic compounds for some time. New products like DOWSIL™ 11-100 Additive not only help with filler dispersion, but can also help improve fire retardant properties of magnesium hydroxide filled halogen-free polyolefin compounds. In addition, treated fillers will absorb less moisture resulting in more durable products with better dielectric properties. Silane dispersing agents can also help reduce the effort and energy needed in the compounding operation.

Fiberglass-reinforced polymers

Silane coupling agents are a critical component of fiberglass-reinforced polymers. They provide a stable bond between incompatible, non-bonding organic and inorganic substrates, to effectively treat fiberglass cloth to bind inorganic glass fibers to organic resin. Silane coupling agents are used on fiberglass for general-purpose reinforced plastic applications, such as automotive, marine, sporting goods and building construction, as well as for high-performance applications in printed circuit boards and aerospace composites.

Product name	Functionality	Chemical description	Application/features	Applications										
				Thermoplastic				Thermosets			Fiberglass	Polymer modification	Surface treatment	
				Filler dispersion	Reinforcement coupling	Adhesion promotion	Crosslinking	Reinforce glass composites	Reinforce coupling	Adhesion promotion	Surface modification	Adhesion promotion primer		
DOWSIL™ 11-100 Additive	Alkyl	Alkyl functional siloxane	Filler dispersion aid with extended shelf life • Impart hydrophobicity to inorganic filler surface • Improve inorganic filler de-agglomeration	•										
XIAMETER™ OFS-6011 Silane	Amino/Ethoxysilane	Aminopropyltriethoxysilane; H ₂ NC ₃ H ₆ -Si(OCH ₂ H ₅) ₃	Coupling agent for thermoset resins with glass or mineral fillers					•						
XIAMETER™ OFS-6020 Silane	Amino/Methoxysilane	Aminoethylaminopropyltrimethoxysilane; H ₂ NC ₂ H ₄ NHC ₂ H ₅ -Si(OCH ₃) ₃	Coupling agent for many thermoset and thermoplastic resins with glass or mineral fillers		•				•					•
XIAMETER™ OFS-6030 Silane	Methacryl/Methoxysilane	Methacryloxypropyltrimethoxysilane; H ₂ C=CH(CH ₃)C(O)OC ₃ H ₇ -Si(OCH ₃) ₃	Coupling agent for many thermoset and thermoplastic resins with glass or mineral fillers		•				•	•				•
XIAMETER™ OFS-6032 Silane	Amino/Vinyl/Methoxysilane	Vinylbenzylaminoethylaminopropyltrimethoxysilane; (H ₂ C=CHC ₆ H ₄ -CH ₂ -NHC ₂ H ₄ NHC ₂ H ₅ -Si(OCH ₃) ₃); HCl 40% in methanol	Coupling agent for many resin systems • Useful for fiberglass-reinforced printed circuit boards • Improved adhesion of organic polymer to inorganic substrate or filler • Improved wet and dry physical properties of composite • Improved mixing and compatibility of filled systems • Compatible with epoxies, polyolefins polymer types	•	•	•		•	•	•	•	•		•
DOWSIL™ Z-6269 Silane	Amino/Vinyl/Methoxysilane	Cationic vinylbenzyl and amino functional methoxy-silane; 40% actives in methanol; Higher actives purity version	Coupling agent for many resins systems • Useful for fiberglass-reinforced printed circuit boards • Improved adhesion of organic polymer to inorganic substrate or filler • Improved wet and dry physical properties of composite • Improved mixing and compatibility of filled systems • Compatible with epoxies for printed circuit boards (PCBs), polyolefins, most polymer types	•	•	•		•	•	•	•	•		•
DOWSIL™ Z-6132 Silane	Amino/Vinyl/Methoxysilane	Hydrolyzed version of XIAMETER™ OFS-6032 Silane; 37% solids in methanol; Similar to XIAMETER™ OFS-6032 Silane	Prehydrolyzed — may improve customer productivity • Compatible with epoxies for PCBs					•				•		
XIAMETER™ OFS-6224 Silane	Amino/Vinyl/Methoxysilane	Vinylbenzylaminoethylaminopropyltrimethoxy silane; (H ₂ C=CHC ₆ H ₄ -CH ₂ -NHC ₂ H ₄ NHC ₂ H ₅ -Si(OCH ₃) ₃); Partially hydrolyzed at 33% in methanol; Low chloride; Similar to XIAMETER™ OFS-6032 Silane	Prehydrolyzed with reduced Cl content					•				•		
XIAMETER™ OFS-6062 Silane	Mercapto/Methoxysilane	3-Mercaptopropyltrimethoxysilane; HS(CH ₂) ₃ Si(OCH ₃) ₃	Coupling agent to improve the adhesion of sulfur-cured elastomers to inorganic fillers, fiberglass and surfaces; treated fillers compatible with epoxy, polysulfide, EPDM, natural rubber, SBR, nitrile rubber		•	•			•		•			
XIAMETER™ OFS-6040 Silane	Epoxy/Methoxysilane	Glycidoxypropyltrimethoxysilane; CH ₂ (O)CHCH ₂ OC ₃ H ₇ -Si(OCH ₃) ₃	Used for silica treatment for EMC application					•	•					•
DOWSIL™ Z-6883 Silane	Phenyl/Amino/Methoxysilane	Phenylaminopropyl trimethoxysilane; PhNHC ₃ H ₇ Si(OCH ₃) ₃	Adhesion promoter for EMC • Improved adhesion between metal and resin and inorganic fillers and resin							•	•			
DOWSIL™ Z-6137 Silane	Amino/Silanol	Aminoethylaminopropylsilane triol homopolymer; H ₂ NC ₂ H ₄ NHC ₂ H ₅ -Si(OH) ₃ ; In water 22% actives; Low methanol content	Adhesion promoter • Coupling agent • Resin additive • Improves chemical bonding of resins to inorganic material			•						•		•
DOWSIL™ Z-6121 Silane	Amino/Alkoxysilane	Aminoethylaminopropyltrimethoxysilane; H ₂ NC ₂ H ₄ NHC ₂ H ₅ -Si(OCH ₃) ₃ ; 50% actives in n-butanol/methanol	Improves chemical bonding of resins to inorganic material			•								•
DOWSIL™ Z-6701 Silane	Methyl/Hydrogen/Methoxysilane	Methyldimethoxysilane; CH ₃ Si(H)(OCH ₃) ₂	Reactive in hydrosilation to form methoxysilyl functional materials • Polymer modification for adhesives and sealants				•						•	



[Back to Table of Contents](#)

Paints, inks and coatings

The unique capabilities of silanes make them ideal for high-performance paints and coatings, as do their ability to withstand physical, chemical, environmental and thermal degradation. They can be used in waterborne or solventborne formulations, are compatible with most binder systems, are suitable for low-VOC, sustainably formulated products and are versatile and easy to use.

The use of silanes in coatings can provide improvements in adhesion; resistance to moisture, chemicals, ultraviolet (UV) rays and abrasion; and improved dispersion of fillers. Silanes are also used as intermediates to produce silicates and siliconates via reaction with metal hydroxide. These materials are used in protective finishes, such as zinc-rich primers, masonry treatments for water repellency, or compounded directly into concrete coatings for improved physical properties and water repellency.

Primers

Silanes provide crucial functionality in the primer segment because they allow formulas to be tailored to specific application performance requirements, enhance adhesion and also offer controlled water resistance, UV and thermal stability, surface activity, chemical resistance and corrosion protection.

Automotive clearcoats


Color-plus-clear coating systems have become the standard for automotive finishes. These coatings deliver outstanding gloss and image distinctiveness, however they are often subjected to damage from environmental elements like stone chipping and abrasive scratching. The inclusion of a surface-reactive silane coupling agent has been shown to improve scratch resistance.

Architectural coatings

Including alkoxysilanes in coating formulations can create a more tightly crosslinked, water resistant film that is much less susceptible to moisture attack. The inclusion of silanes can also improve adhesion, abrasion resistance, thermal stability and durability, pigment and filler dispersion, UV resistance and water and chemical resistance.

Industrial coatings

Combining the cure profiles and barrier properties of organic resins with the thermal and UV stability of silanes, formulators have created high-performance coatings with excellent resistance to corrosion and chemical attack as well as thermal and UV degradation. Some of the benefits achieved with silanes include high heat resistance, excellent mechanical strength and improved water and moisture resistance.

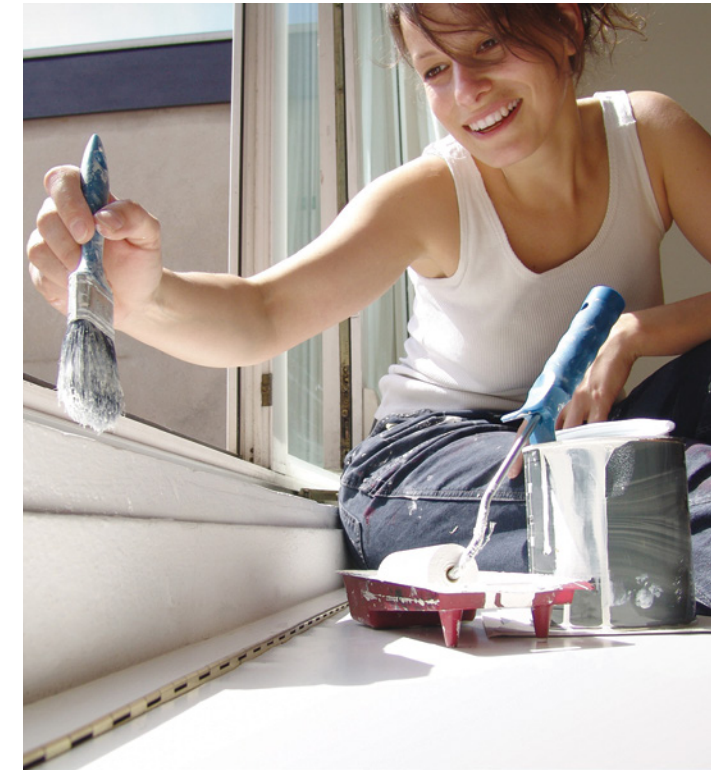

Product name	Functionality	Chemical description	Application/features	Applications							
				Primer	Additive	Pigment treatment		Adhesion promoter			FDA compliant
						Solvent	Waterborne	Solvent	Waterborne	Radiation-cured	
XIAMETER™ OFS-6011 Silane	Amino/Ethoxy-silyl	Aminopropyltriethoxysilane; APTES; 99% actives	Coupling agent for many thermoset and thermoplastic resins and/or adhesion promoter				•	•	•	•	•
XIAMETER™ OFS-6020 Silane	Amino/Methoxy-silyl	Aminoethylaminopropyltrimethoxysilane; 99% actives	Coupling agent for many thermoset and thermoplastic resins and/or adhesion promoter	•		•	•	•	•		•
XIAMETER™ OFS-6030 Silane*	Methacrylate/Methoxy-silyl	3-Methacryloxypropyltrimethoxysilane; 98% actives	Coupling agent for unsaturated resin systems	•	•			•	•	•	•
XIAMETER™ OFS-6032 Silane	Amino/Vinylbenzyl/Methoxy-silyl	Cationic vinylbenzyl and amino-functional methoxy-silane; 40% actives	Coupling agent to improve adhesion of organic resins to inorganic surfaces (e.g. epoxy based print circuit board)	•	•			•	•		•
XIAMETER™ OFS-6040 Silane*	Epoxy/Methoxy-silyl	Glycidoxypropyltrimethoxysilane; 99% actives	Coupling agent for various thermoset resins with glass or mineral	•	•	•	•	•	•		•
DOWSIL™ Z-6121 Silane	Amino/Alkoxy-silyl	Aminoethylaminopropyltrialkoxysilane; 50% actives	Adhesion promoter recommended for use with epoxy coatings, silicone-resin based coatings and alkyd finishes • Can be incorporated into epoxy coatings • Room-temperature curing agent for silicone resin-based coatings • Can be used with alkyd coatings • Effective over a wide range of concentrations • Curing agent for silicone resin-based coatings • Eliminates oven cure	•	•			•	•		
DOWSIL™ Z-6137 Silane	Amino/Silanol	Aqueous solution of amino-functional silicone polymers; 22.5% actives	An additive or primer in water-based systems to improve bonding between organic binder and inorganic substrate • Works well with phenols and epoxies — may also work with polyurethanes and acrylics • Low methanol content (<1%)						•		

*When used as a primer, apply by dipping or brushing.



Adhesives and sealants

Silanes are widely used to improve the adhesion of a broad range of sealants and adhesives to inorganic substrates such as metals, glass and stone. The reputation of silane-enhanced sealants and adhesives in the aircraft, automotive and construction industries is built upon their ability to form durable bonds to metal, glass, ceramic and other surfaces – bonds that withstand exposure to heat, ultraviolet radiation, humidity and water.



Adhesion promoters

A silane coupling agent will function at the interface between the sealant or adhesive and the substrate to act as an adhesion promoter. Mixtures of silanes are used as adhesion promoters to provide enhanced water resistance, thermal stability, or crosslinking at the bonding site. The silanes can be blended into an adhesive formulation or used as primers on substrates, resulting in an adhesive bond with greater resistance to moisture attack, longer life and greater temperature and chemical resistance.

Coupling agents

Silane coupling agents are used to increase adhesion between fillers and the polymer matrix in sealants and adhesives. The silane coupling agent treatment on the filler can provide better bonding of the pigment or filler to the resin, improved mixing, increased matrix strength and reduced viscosity of the uncured sealant or adhesive.

Product name	Functionality	Chemical description	Application/features	Primer	Additive
XIAMETER™ OFS-1579 Silane	Alkyl	Methyl and ethyl triacetoxysilanes	Crosslinker for silicone RTVs		●
XIAMETER™ OFS-6070 Silane	Alkyl	Methyltrimethoxysilane; CH ₃ -Si(OCH ₃) ₃ ; MTMS	Crosslinker for silicone RTVs • Moisture scavenger		●
XIAMETER™ OFS-6011 Silane	Amino/Ethoxy-silyl	Aminopropyltriethoxysilane; APTES; 99% actives	Coupling agent for many thermoset and thermoplastic resins and/or adhesion promoter	●	●
XIAMETER™ OFS-6020 Silane	Amino/Methoxy-silyl	Aminoethylaminopropyl-trimethoxysilane; 99% actives	Coupling agent for many thermoset and thermoplastic resins and/or adhesion promoter	●	●
XIAMETER™ OFS-6030 Silane*	Methacrylate/Methoxy-silyl	3-methacryloxypropyl-trimethoxysilane; 98% actives	Coupling agent for unsaturated resin systems	●	●
XIAMETER™ OFS-6040 Silane*	Epoxy/Methoxy-silyl	Glycidoxypropyltrimethoxysilane; 99% actives	Coupling agent for various thermoset resins with glass or mineral	●	●

*When used as a primer, apply by dipping or brushing.



Mineral and filler treatments

The metal hydroxyl groups on the surface of minerals are usually hydrophilic and incompatible with organic polymers. Alkoxysilanes are a natural fit to treat the surface of the mineral to make it more compatible and dispersible in the polymer, or even to make the filler a reinforcing additive. Minerals with silicon and aluminum hydroxyl groups on their surfaces are generally very receptive to bonding with alkoxysilanes.

Silane treatment can improve processing, performance and durability of mineral-modified products by reducing the viscosity of the filler/polymer mix, as well as improving:

- Adhesion between the mineral and polymer
- Wet-out of the mineral by the polymer
- Dispersion of the mineral in the polymer
- Electrical properties
- Mechanical properties

Figure 8: Filler surface treatment



Product name	Functionality	Chemical description	Application/features	Dispersing agent	Reactive treatment
DOWSIL™ 11-100 Additive	Alkyl	Alkyl functional siloxane	Filler dispersion aid with extended shelf life • Impart hydrophobicity to inorganic filler surface • Improve inorganic filler de-agglomeration	•	
XIAMETER™ OFS-6341 Silane	Alkyl	n-Octyltriethoxysilane; $C_8H_{17}Si(OCH_2CH_3)_3$; nOTES	Hydrophobic surface treatment • Organic modification of surfaces • Formulating penetrating treatments that provide water repellency and prevent water absorption into concrete	•	
XIAMETER™ OFS-6011 Silane	Amino/Ethoxysilane	Aminopropyltriethoxysilane; $H_2NC_3H_6-Si(OCH_2CH_3)_3$	Coupling agent for thermoset resins with glass or mineral fillers		•
XIAMETER™ OFS-6020 Silane	Amino/Methoxysilane	Aminoethylaminopropyl-trimethoxysilane; $H_2NC_2H_4NHC_3H_6-Si(OCH_3)_3$	Coupling agent for many thermoset and thermoplastic resins with glass or mineral fillers		•
XIAMETER™ OFS-6030 Silane	Methacryl/Methoxysilane	Methacryloxypropyl-trimethoxysilane; $H_2C=CH(CH_3)C(O)OC_3H_6-Si(OCH_3)_3$	Coupling agent for many thermoset and thermoplastic resins with glass or mineral fillers		•
XIAMETER™ OFS-6040 Silane	Epoxy/Methoxysilane	Glycidoxypropyltrimethoxysilane; $CH_2(O)CHCH_2OC_3H_6-Si(OCH_3)_3$	Used for silica treatment for EMC application		•
XIAMETER™ OFS-6124 Silane	Phenyl	Phenyltrimethoxysilane; $(C_6H_5-Si(OCH_3)_3)$	Hydrophobic surface treatment • Hydrophobic additive to other silane coupling agents • Thermal stability additive to other silanes	•	
XIAMETER™ Q1-6083 Antifreeze Additive	Phosphonate Sodium Siliconate	40% Sodium (trihydroxysilyl)-propylmethylphosphonate in water			• (Engine coolant)

Solutions wherever you need them

Silanes bring performance-enhancing and problem-solving benefits to a wide array of specialty applications. No matter your application, Dow can provide the silane solution and technical support you need.

Based in Midland, Michigan, USA, Dow has manufacturing, customer service and science and technology resources located worldwide, as well as full-service, global technical support. With a full range of silane product and application solutions, Dow offers you innovation, expertise, technical knowledge and a global reach backed with local support.

For more information on our silane selection and capabilities, visit [dow.com/silanes](https://www.dow.com/silanes) or contact us today by visiting [dow.com/contactus](https://www.dow.com/contactus).

[Back to Table of Contents](#)

Images: Cover – dow_41392243225; Page 2 – dow_41392226242; Page 6 – dow_42083546981; Page 11 – dow_42083496788; Page 12 – dow_42083551474

NOTICE: No freedom from infringement of any patent owned by Dow or others is to be inferred. Because use conditions and applicable laws may differ from one location to another and may change with time, Customer is responsible for determining whether products and the information in this document are appropriate for Customer's use and for ensuring that Customer's workplace and disposal practices are in compliance with applicable laws and other government enactments. The product shown in this literature may not be available for sale and/or available in all geographies where Dow is represented. The claims made may not have been approved for use in all countries. Dow assumes no obligation or liability for the information in this document. References to "Dow" or the "Company" mean the Dow legal entity selling the products to Customer unless otherwise expressly noted. NO WARRANTIES ARE GIVEN; ALL IMPLIED WARRANTIES OF MERCHANTABILITY OR FITNESS FOR A PARTICULAR PURPOSE ARE EXPRESSLY EXCLUDED.

®™ Trademark of The Dow Chemical Company ("Dow") or an affiliated company of Dow

© 2021 The Dow Chemical Company. All rights reserved.

2000012520

Form No. 26-2350-01-0821 S2D